

Resource Guide—Chemical Resistance Chart

This information was provided to Freelin-Wade by our suppliers and other sources. It is to be used only as a general reference guide to aid in the selection of products in which chemical and material compatibility issues are a factor. This guide is not intended as a complete nor conclusive database. Freelin-Wade does not guarantee these ratings since the resistance of a material can be greatly affected by the temperature, consistency, and presence of other chemicals. Ultimately, the consumer must determine the chemical compatibility of an item based on the conditions in which the product is being used.

Rating Scale

- 1= Little or no impact
- 2= Minor effect
- 3= Moderate effect
- 4= Severe effect

	PUR	PE	PVC	Nylon	Kynar
Acetic Acid, Glacial	4	2	4	-	1
Acetic Acid, 30%	4	1	4	2	1
Acetone	4	2	4	1	4
Acetylene	1	4	1	1	1
Alkazene	4	-	-	-	-
Aluminum Chloride (aq)	3	2	1	-	1
Aluminum Nitrate (aq)	3	-	2	-	1
Ammonia Anhydrous	4	2	1	-	4
Ammonia Gas (cold)	3	-	3	1	4
Ammonia Gas (hot)	4	-	-	1	4
Ammonium Chloride (aq) 40%	2	1	1	-	1
Ammonium Sulfate (aq)	1	1	1	1	1
Amyl Alcohol	4	2	1	-	1
Amyl Naphthalene	4	-	-	-	-
Animal Fats	1	2	-	-	-
Aqua Regia	4	2	3	-	-
Arsenic Acid	3	2	1	-	1
Asphalt	2	1	1	-	1
ASTM Fuel A	2	-	-	-	-
ASTM Fuel B	3	-	-	-	-
ASTM Fuel C	3	1	4	-	-
Barium Chloride (aq)	1	2	1	1	1
Beer	2	2	1	1	1
Beet Sugar Liquors	4	1	1	-	1
Benzene	3	4	3	1	1
Benzine	2	-	-	-	-
Blast Furnace Gas	4	-	-	-	-
Bleach Solutions	4	1	1	-	1
Borax	1	1	1	-	1
Boric Acid	1	1	1	-	1
Brake Fluid	4	-	-	-	1
Brine	2	-	3	-	1
Bromine Water	4	-	3	4	1
Bunker Oil	2	-	-	-	-
Butane	1	3	3	1	1
Butter	1	-	-	-	-
Butyl Alcohol (Butanol)	3	1	3	1	1
Butylene	4	1	1	-	1
Calcium Chloride (aq)	1	1	3	1	1
Calcium Hydroxide (aq)	2	1	2	-	1
Calcium Nitrate (aq)	1	-	1	1	1
Calcium Sulfide (aq)	1	-	-	-	-
Cane Sugar Liquors	4	-	1	-	1
Carbolic Acid	3	4	3	-	-
Carbon Dioxide	1	2	1	-	1
Carbonic Acid	4	2	1	-	-
Carbon Monoxide	1	2	1	-	1
Carbon Tetrachloride	4	4	4	3	1
Castor Oil	1	1	1	-	1
Chlorine (dry)	4	3	4	4	1
Chlorine (wet)	4	3	-	4	1
Chloroform	4	4	4	3	1
Chlorox	4	-	-	-	-
Chromic Acid 50%	4	1	4	4	1
Citric Acid	1	1	2	1	1
Coal Tar (Creosote)	3	-	-	-	-
Coconut Oil	2	1	1	-	1
Cod Liver Oil	1	1	1	-	-
Coke Oven Gas	4	-	-	-	-
Copper Chloride (aq)	1	2	1	-	1
Copper Cyanide (aq)	1	2	1	-	1
Corn Oil	1	1	2	-	1
Cotton Seed Oil	1	1	2	-	1
Creosol (Methyl Phenol)	4	4	4	4	1
Cyclohexane	1	4	4	1	1
Denatured Alcohol	4	-	-	-	-
Detergent Solution	3	1	1	-	-
Diesel Oil	2	3	1	-	-
Dioxane	4	3	-	-	4
Dowtherm Oil	3	-	-	-	-
Dry Cleaning Fluids	4	-	-	-	-
Ethane	1	-	1	-	-
Ethyl Acrylate	4	-	-	-	1
Ethyl Alcohol (Ethanol)	4	2	3	3	1
Ethyl Benzene	4	-	-	-	-
Ethyl Cellulose	2	-	-	-	-
Ethyl Chloride	4	4	4	-	1
Ethyl Ether	3	4	4	-	1
Ethylene Chloride	4	4	4	-	-
Ethylene Glycol ² (Anti-Freeze)	2	1	1	1	1
Ethylene Oxide	4	3	3	1	1
Ethylene Trichloride	4	4	-	-	-
Ferric Chloride (aq)	1	2	1	-	1
Ferric Nitrate (aq)	1	2	1	-	1
Ferric Sulfate (aq)	2	1	1	-	1
Fluorine (Liquid)	4	3	4	4	1
Formaldehyde (RT)	4	2	1	1	1
Formic Acid	4	2	1	4	1
Freon 11	4	3	1	-	-
Freon 12	1	1	1	1	-
Freon 22	4	-	1	1	-
Fuel Oil (Bunker 'C')	2	3	1	-	1
Gasoline (100 Octane, High Test)	3	4	3	1	1
Glue	1	1	3	-	1
Glycerin (Glycerol)	1	1	1	1	1
Glycols	4	-	-	1	-
Green Sulfate Liquor	1	-	-	-	-
Hexane	2	4 ¹	2 ²	-	1
Hydraulic Oil	1	1-3	1	-	-
Hydrochloric Acid (cold) 37%	4	2	2	4	1
Hydrochloric Acid (hot) 37%	4	-	-	4	1
Hydrofluoric Acid (Conc.) (cold)	4	2	-	-	1
Hydrofluoric Acid (Conc.) (hot)	4	-	-	-	1
Hydrogen Gas	1	1	1	1	1
Isobutyl Alcohol	3	1	-	-	1
Isocetane	2	3	1	-	1
Isopropyl Acetate	4	3	4	-	-
Isopropyl Alcohol (Isopropanol)	3	1	-	1	1
Isopropyl Ether	2	1	2	-	-
Kerosene	1	4	2	1	1

	PUR	PE	PVC	Nylon	Kynar
Lacquers	4	1	4	-	-
Lacquer Solvents	4	1	3	-	-
Lard	1	1	1	-	1
Lavender Oil	4	-	-	-	-
Lead Acetate (aq)	4	1	1	-	1
Linseed Oil	2	3	1	1	1
Lubricated Petroleum Gas	1	-	-	1	-
Lubricating Oils	1-2 ³	4	2	1	1
Lye	4	1-4 ⁴	1-2	-	-
Magnesium Chloride (aq)	1	2	1	1	1
Magnesium Hydroxide (aq)	4	2	1	-	1
Mercury	1	1	1	1	1
Methane	3	-	2	1	1
Methyl Acetate	4	2	4	1	1
Methyl Acrylate	4	-	-	-	1
Methyl Alcohol (Methanol)	4	1	1	1	1
Methyl Butyl Ketone	4	-	1	-	-
Methyl Chloride	4	4	4	1	1
Methylene Chloride	4	4	4	-	1
Methyl Ethyl Ketone	4	2	4	1	4
Methyl Isobutyl Ketone	4	3	4	1	4
Milk	4	1	1	1	1
Mineral Oil	1	3	1	1	1
Motor Oil 20W, 10W40	2	3	2	1	1
Naphtha (Lighter Fluid)	2	4	1	1	1
Naphthalene (Moth Repellent)	2	2	4	1	1
Natural Gas	2	-	1	-	1
Neatsfoot Oil	1	-	-	-	-
Nitric Acid 70%	4	2	-	4	1
Nitric Acid (Dilute) 10%	3	2	1	4	1
Nitroethane	4	-	-	-	1
N-Octane	4	1	-	-	1
Oleic Acid	2	1	3	1	1
Oleum Spirits	3	4	4	-	4
Olive Oil	1	1	-	-	1
Oxygen (cold)	1	-	-	1	1
Oxygen (200-400F)	4	-	-	-	-
Paint Thinner, Duco	4	-	-	-	-
Perchloric Acid	4	1	3	-	1
Perchloroethylene	4	4	3	3	1
Petroleum - Below 250F	2	3	-	-	1
Petroleum - Above 250F	4	-	-	4	-
Phenol (Carbolic Acid)	3	2	3-4	4	1
Phenyl Ethyl Ether	4	-	-	-	-
Phosphoric Acid - 45%	4	1	2	2	1
Pickling Solution	4	-	-	-	-
Picric Acid	2	1	4	3	1
Potassium Acetate (aq)	4	-	-	-	1
Potassium Chloride (aq)	1	2	1	-	1
Potassium Cyanide (aq)	1	2	1	-	1
Potassium Hydroxide (aq)	4	1	1	3	4
Producer Gas	1	1	1	-	-
Propane	1	4	1	1	1
Propyl Alcohol (Propanol)	4	1	1	-	1
Propylene	4	-	2	-	-
Propylene Glycol (Anti-Freeze)	3	1	3	2	1
Propylene Oxide	4	2	-	-	4
Pydraul, 10E, 29 ELT	4	-	-	-	-
Pydraul 30E, 50E, 65E	4	-	-	-	-
Pydraul, 115E	4	-	-	-	-
Pydraul 230E, 312C, 540C	4	-	-	-	-
Rapeseed Oil	2	4	-	-	-
RJ-1 (MIL-F-23338 B)	1	-	-	-	-
RP-1 (MIL-F-23576 C)	1	-	-	-	-
Salt Water	2	1	1	1	1
Sewage	1	-	-	-	1
Silicate Esters	1	-	-	-	-
Silicone Oils	1	1	1	-	1
Silver Nitrate	1	1	1	-	1
Skydrol 500	4	-	-	-	-
Skydrol 700	4	-	-	-	-
Soap Solutions	3	4	1	1	-
Sodium Chloride (aq)	1	1	1	1	-
Sodium Hydroxide (aq)	4	1	1	2	4
Sodium Peroxide (aq)	4	1	2	-	1
Sodium Phosphate (aq)	1	-	-	-	1
Sodium Sulfate (aq)	1	1	1	-	-
Soy Bean Oil	2	1	1	-	1
Stoddard Solvent	1	3	3	-	-
Styrene (Monomer)	4	-	4	1	1
Sucrose Solution	4	2	-	-	-
Sulfuric Acid (Dilute Battery Acid)	3	1	1	-	1
Sulfuric Acid (Conc)	4	2	4	-	1
Sulfuric Acid (20% Oleum)	4	-	4	-	4
Sulfurous Acid	4	2	1	-	-
Tannic Acid	4	1	1	-	1
Tetrachlorethylene	4	2	4	-	-
Toluene (Toluol)	4	3	4	1	1
Transformer Oil	2	-	2	-	-
Transmission Fluid Type A	2	-	-	-	-
Trichloroethane	4	4	3	3	1
Trichloroethylene	4	4	4	3	1
Turbine Oil	1	3	1	1	-
Turpentine	4	4	4	1	1
Varnish	3	3	4	-	1
Vinegar	2	1	1	1	1
Vinyl Chloride	4	4	4	-	1
Water	1	1	1	1	1
Whiskey, Wines	2	1	1	1	1
White Oil	1	-	-	-	-
Wood Oil	3	-	-	-	-
Xylene	4	4	4	1	1
Zinc Acetate (aq)	4	-	-	-	1
Zinc Chloride (aq)	2	1	1	1	1

1 Petroleum Base 2 Synthetic Base = 1, Petroleum Base = 3

3 SAE 10, 20, 30, 40, 50 = 1, Petroleum = 2

4 Calcium Hydroxide & Potassium (Hydroxide=1, Sodium


Hydroxide=4) 5 See Propylene Glycol 6 See Ethylene Glycol

Part Number Index & Tubing Pressure Guide

Part Number	Page	Part Number	Page	Part Number	Page	Part Number	Page	Part Number	Page	Part Number	Page
10A-025-00	36	1A-458-	25	1B-68-	19	1J-015-	10	1J-194-	10	3A-022-	35
10E-025-00	36	1A-472-	25	1B-69-	19	1J-025-	10	1J-20-	15	3A-028-	35
1A-005-	10	1A-486-90-	25	1B-90_-10	19	1J-030-	10	1J-21-	15	3J-022-	35
1A-013-	10	1A-488-90-	25	1B-94_-10	19	1J-045-	10	1J-22-	16	3J-028-	35
1A-015-	10	1A-489-90-	25	1B-96_-10	13	1J-048-	12	1J-24-	15	3W-022-	35
1A-025-	10	1A-490-90-	25	1C-013-	10	1J-071-	13	1J-26-	17	4A-023-	35
1A-030-	10	1A-491-90-	25	1C-030-	10	1J-072-	13	1J-27-	17	4A-026-	35
1A-045-	10	1A-68_-	19	1C-109-	12	1J-073-	13	1J-28_-10	17	4J-023-	35
1A-048-	12	1A-69_-	19	1C-134-	10	1J-074-	12	1J-35_-07	23	4J-026-	35
1A-071-	13	1A-70_-10	11	1C-15_-	9	1J-075-	13	1J-36_-07	23	4M_-	20/21
1A-072-	13	1A-80_-10	27	1C-171-	9	1J-076-	12	1J-37_-	22	4ME_-	20/21
1A-073-	13	1A-90_-10	19	1C-189-	12	1J-077-	12	1J-38_-	22	4W-023-	35
1A-074-	12	1A-94_-10	19	1C-20_-	15	1J-078-	36	1J-39_-	22	6M_-	20/21
1A-075-	13	1A-96_-10	13	1C-22_-	16	1J-107-	9	1J-458-	25	6ME_-	20/21
1A-076-	12	1AA-075-	13	1C-26_-	17	1J-109-	12	1J-488-90_-	25	8M_-	20/21
1A-077-	12	1AA-076-	12	1C-246-	15	1J-111-	10	1J-68_-	19	8ME_-	20/21
1A-078-	36	1AA-086-	12	1C-413-	25	1J-12_-01	36	1J-69_-	19	HTC-	37
1A-086-	12	1AA-207-	15	1C-430-	25	1J-132-	10	1J-7_-10	11	N106_-	33
1A-107-	9	1AA-213-	15	1C-457-90-	25	1J-133-	10	1J-90_-10	19	N12_-	32
1A-109-	12	1AA-245-	15	1C-486-90-	25	1J-134-	10	1J-94_-10	19	N14_-	32
1A-111-	10	1AA-248-	15	1C-68_-	19	1J-149-	10	1J-96_-	13	N17_-	33
1A-132-	10	1AA-267-	17	1C-900-10	19	1J-151-	9	1L-013-	10	N38_-	32
1A-133-	10	1AA-275-	17	1C-94_-10	19	1J-152-	9	1L-109-	12	PFE_-	28
1A-134-	10	1AA-284-10	17	1C-96_-	13	1J-153-	10	1L-157-	9	PR_-	31
1A-149-	10	1AA-684-10	19	1D-025-	10	1J-156-	9	1L-189-	12	PRE_-	29
1A-151-	9	1B-005-	10	1D-078-	36	1J-157-	9	1W_-	34	PTC_-	37
1A-152-	9	1B-013-	10	1D-12_-01	36	1J-158-	9	1X_-	34	PU14_-	30
1A-153-	10	1B-025-	10	1E-0_-	27	1J-159-	9	1Y_-	34	PU316_-	30
1A-156-	9	1B-030-	10	1E-176-	9	1J-160-	9	1Z_-	34	PU38_-	30
1A-157-	9	1B-045-	10	1E-501-	27	1J-161-	9	2A_-	35	PU516_-	30
1A-158-	9	1B-048-	12	1E-625-	27	1J-162-	9	2B-006-	35	PUE_-	29
1A-159-	9	1B-68_-	19	1E-80_-	27	1J-163-	9	2J_-	35	PXC_-	36/37
1A-160-	9	1B-071-	13	1F-0_-	27	1J-166-	9	2M_-	20/21	TC_-	37
1A-161-	9	1B-107-	9	1F-501-	27	1J-169-	9	2MC-	21	TMC_-	37
1A-162-	9	1B-109-	12	1F-625-	27	1J-170-	10	2ME-	20/21		
1A-163-	9	1B-126-01	36	1J-005-	10	1J-171-	9	2V-006-	35		
1A-166-	9	1B-127-01	36	1J-013-	10	1J-189-	12	2W-016-	35		
1A-169-	9	1B-128-01	36								
1A-170-	10	1B-132-	10								
1A-171-	9	1B-133-	10								
1A-176-	9	1B-15_-	9								
1A-189-	12	1B-169-	9								
1A-194-	10	1B-171-	9								
1A-20_-	15	1B-189-	12								
1A-214-	15	1B-194-	10								
1A-22_-	16	1B-20_-	15								
1A-24_-	15	1B-22_-	16								
1A-26_-	17	1B-24_-	15								
1A-27_-	17	1B-26_-	17								
1A-28_-	17	1B-27_-	17								
1A-35_-07	23	1B-28_-10	17								
1A-36_-07	23	1B-35_-07	23								
1A-37_-	22	1B-37_-	22								
1A-38_-	22	1B-39_-	22								
1A-39_-	22	1B-413-	25								
1A-405-	25	1B-425-	25								
1A-413	25	1B-430-	25								
1A-425-	25	1B-451-90-	25								
1A-430-	25	1B-457-90-	25								
1A-451-90-	25	1B-458-	25								
1A-452-90-	25	1B-486-90-	25								
1A-457-90-	25	1B-488-90_-	25								

Working Pressure at Elevated Temperatures

To be used for reference only

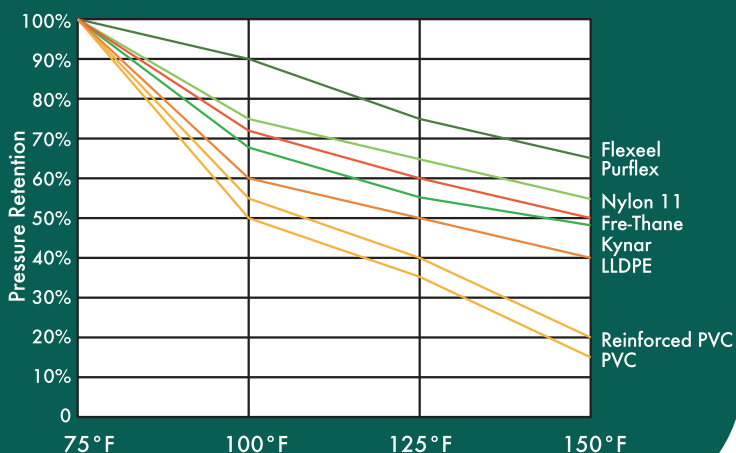

Doing everything we can to say **"YES"** to your tubing needs

For more than 33 years our customers have looked to Freelin-Wade to solve their specific tubing requirements. We manufacture and stock more than 4,000 tubing products made from polyurethane, nylon, LLDPE, PVC and many other plastic resins. Many options are FDA, USPVI, NSF51 and/or NSF61 compliant. Much of our business is comprised of taking this stock tubing and adapting it to meet our customers' needs. We call these "Variations." Variations can come in many forms including:

- Assembly
- Bonding
- Coiling
- Colors
- Cutting
- Forming
- Jacketing
- Packaging
- Printing
- Sizes

We provide design expertise and rapid prototyping options. We set the industry standard for tubing that fits and arrives on time.



1730 NE Miller Street
McMinnville, Oregon 97128
United States of America
©2014
888-373-9233
www.freelin-wade.com